

INCH-POUND

MIL-DTL-26666F
23 April 2004
SUPERSEDING
MIL-DTL-26666E
26 April 1999

DETAIL SPECIFICATION

HOSE ASSEMBLY, PNEUMATIC, HIGH PRESSURE

This specification is approved for use by all Departments and Agencies of the Department of Defense.

1. SCOPE

1.1 Scope. This specification covers the requirements for a pneumatic hose assembly having a nominal working pressure of 4,000 psig in the operating temperature range of -65 to +160°F. DO NOT USE FOR OXYGEN. DO NOT USE ON AIRCRAFT.

2. APPLICABLE DOCUMENTS

2.1 General. The documents listed in this section are specified in sections 3, 4, or 5 of this specification. This section does not include documents cited in other sections of this specification or recommended for additional information or as examples. While every effort has been made to ensure the completeness of this list, document users are cautioned that they must meet all specified requirements documents cited in sections 3, 4, or 5 of this specification, whether or not they are listed.

Comments, suggestions, or questions on this document should be addressed to Defense Supply Center, Columbus, ATTN: DSCC-VAI, P.O. Box 3990, Columbus, OH 43216-5000, or email to Construction@dsc.dla.mil. Since contact information can change, you may want to verify the currency of this address information using the ASSIST Online database at <http://www.dodssp.daps.mil>.

2.2 Government documents.

2.2.1 Specifications, standards, and handbooks. The following specifications, standards, and handbooks form a part of this document to the extent specified herein. Unless otherwise specified, the issue of these documents are those cited in the solicitation or contract.

DEPARTMENT OF DEFENSE STANDARDS

- MIL-STD-889 - Dissimilar Metals
- AN818 - Nut, Tube Coupling, Short

(Copies of these documents are available online at <http://assist.daps.dla.mil/quicksearch/> or <http://www.dodssp.daps.mil> or from the Standardization Document Order Desk, 700 Robbins Avenue, Building 4D, Philadelphia, PA 19111-5094.)

2.3 Non-Government publications. The following documents form a part of this document to the extent specified herein. Unless otherwise specified, the issues of these documents are those cited in the solicitation or contract.

ASTM INTERNATIONAL

- ASTM D1248 - Polyethylene Plastics Extrusion Materials for Wire and Cable
- ASTM D2000 - Rubber Products in Automotive Applications

(Copies of these documents are available from <http://www.astm.org> or ASTM International, 100 Barr Harbor Drive, West Conshohocken, PA 19428-2959.)

SAE INTERNATIONAL

- SAE AMS-QQ-P-35 - Passivation Treatment for Corrosion – Resistant Steel
- SAE ARP908 - Hose and Tube Fitting, Installation and Qualification Test Torque Requirements
- SAE AS4395 - Tube Connection, Fitting End-Flared, Design Standard
- SAE AS8879 - Screw Threads, Controlled Radius Root with Increased Minor Diameter, General Specification for

(Copies of these documents are available from <http://www.sae.org> or SAE International, 400 Commonwealth Drive, Warrendale, PA 15096-0001.)

2.4 Order of precedence. In the event of a conflict between this text of this document and the references cited herein, the text of this document takes precedence. Nothing in this document, however, supersedes applicable laws and regulations unless a specific exemption has been obtained.

3. REQUIREMENTS

3.1 First article. When specified (see 6.2), samples shall be subjected to first article inspection in accordance with 4.3.

3.2 Materials. Materials shall be as identified herein or as approved by the acquiring activity. However, when a specific material is not specified, a material shall be used which will enable the hose assemblies to meet the performance requirements of this specification. Acceptance or approval of any constituent material shall not be construed as a guarantee of acceptance of the finished product.

3.2.1 Hazardous substances. The use of hazardous substances, toxic chemicals, or Ozone Depleting Chemicals (ODCs) shall be avoided, whenever feasible.

3.2.2 Fungus proof materials. Materials which are not nutrients for fungi shall be used to the greatest extent practicable without effecting performance. Where materials that are nutrients for fungi must be used, such materials shall be treated with a fungicidal agent to render the material fungus-resistant.

3.2.3 Rubber products. Rubber products, such as, seals, covers, and friction layers shall be fabricated from rubber components conforming to ASTM D2000.

3.2.4 Dissimilar metal. Unless protected against electrolytic corrosion, dissimilar metals shall not be used in intimate contact with each other. Dissimilar metals are defined in MIL-STD-889.

3.3 Design and construction. The hose assembly shall consist of a hose with a seamless inner tube, reinforced with corrosion resistant steel wire coupled with corrosion resistant steel end fittings, and a protective outer cover. The hose assembly shall be designed for a pneumatic working pressure of 4,000 psig in an operating temperature range of -65 to +160°F.

3.3.1 Hose. The hose shall be constructed with a seamless inner tube reinforced with corrosion resistant wire and capable of retaining end fittings without slippage or leakage.

3.3.1.1 Inner tube. The inner tube shall consist of a high density polyethylene compound of seamless construction and uniform gage. It shall be compounded and processed to permit the least amount of effusion of compressed gases consistent with the requirements specified herein. The uncompounded polyethylene material shall conform to ASTM D1248, type 3. The inner tube shall have a smooth bore, be free from pitting and other defects, and free of any foreign material or lubricants.

3.3.1.2 Reinforcement. The reinforcement shall consist of two or more spirally wrapped or braided (or combination there-of) plies of high tensile steel wires. Reinforcement separation materials, if used, shall permit gas effusion from the inner tube to escape to the atmosphere. There shall be no broken or spliced reinforcing wires nor shall any wires be omitted in any length of hose.

3.3.1.3 Outer protective cover. An outer protective cover extending the full length of the hose, 0.125 (3.175 mm) to 0.250 inch (6.35 mm) from the end of the fitting, shall be furnished on the outside of the hose. The cover shall be a minimum of 0.0625 inch (1.59 mm) thick, consist of an abrasion-, oil-, and ozone-resistant chloroprene polymer or equivalent synthetic material compounded to meet the requirements specified herein. The cover need not be bonded to the outer-most reinforcement ply, but shall not be free to slip or turn along the length of hose. The cover shall permit gas that may effuse from the inner tube to escape to the atmosphere.

3.3.1.4 Diameter. The inside and outside diameters of the hose shall be within the limits shown on figure 1 as applicable to the hose size specified by the acquiring activity (see 6.2).

3.3.1.5 Length. The hose assembly shall be furnished in lengths as specified by the acquiring activity (see 6.2). The hose assembly length shall be measured as shown on figure 1.

3.3.2 End fittings. The hose assembly end fittings shall conform to the general configuration shown on figure 1, shall be made of corrosion resistant steel, and shall mate with the fitting conforming to SAE AS4395 corresponding to the hose size. The swivel nut dimensions across flats shall conform to an applicable size of AN818. Provisions for wrenching by a hex or flats on fitting body shall be optional. The nipple bore diameter shall conform to the limits shown on figure 1. The end fitting shall be designed for a working pressure of 4,000 psig and a minimum burst pressure of 16,000 psig. The end fittings shall be retained on the assembly without slipping or leaking when coupled to the hose and tested as specified herein.

3.3.3 Jump sizes. When specified (see 6.2), the hose assembly shall be supplied with an end fitting of a different nominal size than the hose itself. In such cases, the end fitting swivel nut and nipple shall mate with fittings conforming to SAE AS4395 for the specified jump size while the fitting body and nipple bore diameter shall conform to the applicable dimensions for the specified nominal hose size

3.3.4 Fitting guard. When specified (see 6.2), a fitting guard shall be securely attached to each end of the hose assembly to restrict the hose bend angle at the fitting. The fitting guard shall have less flexibility than the hose and encase the ends of the hose and fitting.

3.4 Performance.

3.4.1 Visual examination and dimensional check.

3.4.1.1 Visual examination. The hose assembly shall conform to the requirements of this specification when visually examined as specified in 4.6.1.1.

3.4.1.2 Dimensional check. The hose assembly shall be in accordance with figure 1 when dimensionally checked as specified in 4.6.1.2.

3.4.2 Proof pressure. The hose assembly shall not show any evidence of leakage, distortion or material failure, when tested as specified in 4.6.2.

3.4.3 Leakage. The hose assembly shall not leak when subjected to a pneumatic pressure of 4,000 psig, when tested as specified in 4.6.3.

3.4.4 Cold temperature flexing. The hose assembly shall not show any evidence cracking, splitting, distortion, or leakage when tested as specified in 4.6.4.

3.4.5 Elongation and contraction. The change in hose length shall be within ± 3 percent, when tested as specified in 4.6.5.

3.4.6 Tensile strength. The hose assembly shall not show any evidence of material failure from a tensile pull of not less than 1,000 pounds, when tested as specified in 4.6.6.

3.4.7 Burst pressure. The hose assembly shall not burst or show any evidence of material failure at less than 16,000 psi pressure, when tested as specified in 4.6.7.

MIL-DTL-26666F

3.4.8 Overtightening torque. The end fitting of the hose assembly shall not show any evidence of material failure, thread damage, deformation or difficulty in turning the swivel nut on the nipple by hand, when tested as specified in 4.6.8

3.4.9 Pressure impulse cycling. The hose assembly shall not show any evidence of cracking, splitting, distortion, or leakage, when tested as specified in 4.6.9.


3.4.10 Cleanliness. The hose assembly shall not contain any particle size larger than 30 microns or a total residue weight greater than one milligram per milliliter of the measured fluid sample, when tested as specified in 4.6.10.

3.5 Screw threads. All coupling nut threads shall be in accordance with SAE AS8879.

3.6 Identification of product. The hose assembly shall be identified by a permanently snug-fitting aluminum or stainless steel band around the hose near the end fitting. The band shall be designed to remain tight on the hose to prevent relative movement and resultant chafing. Where the hose assembly exceeds 4 feet in length, a band shall be attached near each end fitting of the assembly. The metal band shall be marked in raised, etched, or stamped lettering with the following information appropriately identified:

- a. Number and title of this specification.
- b. DO NOT USE ON AIRCRAFT
- c. Date of assembly in month and year.
- d. The rated working pressure in psi, followed by the word PNEUMATIC.
- e. Manufacturer's name and trademark.
- f. Manufacturer's Part or Identifying Number (PIN).
- g. Hose manufacturer's cage code if different from hose assembly manufacturer.

MIL-DTL-26666F

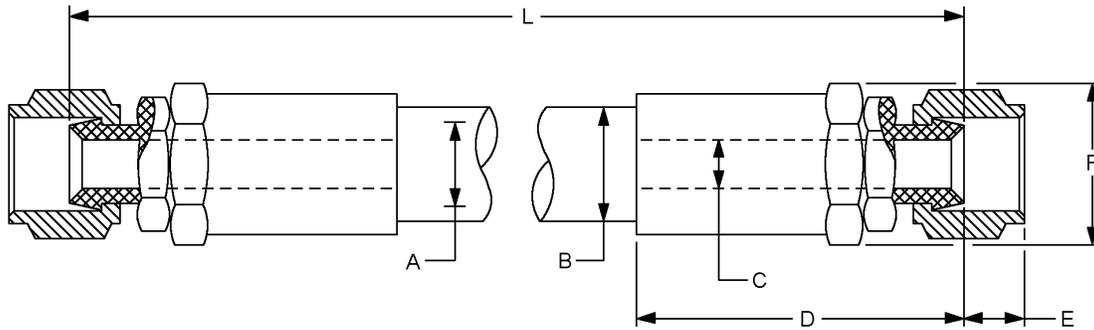

Dash size (to mate with SAE AS4395)	Tube ID	A hose ID min (mm)	B hose OD max (mm)	C coupling ID min (mm)	D (max) (mm)	E (mm)		F (DIA) (max) (mm)	Hose min. inside bend rad (mm)
04	1/4	0.234 (5.94)	0.703 (17.86)	0.125 (3.18)	2.100 (53.34)	0.375 (9.53)	±0.015 (0.38)	0.875 (22.23)	3.250 (82.55)
06	3/8	0.297 (7.54)	0.859 (21.82)	0.188 (4.78)	2.470 (62.74)	0.375 (9.53)		1.160 (29.46)	5.250 (133.35)
08	1/2	0.422 (10.72)	1.000 (25.40)	0.297 (7.54)	2.730 (69.34)	0.438 (11.13)		1.375 (9.53)	6.000 (152.40)
10	5/8	0.547 (13.89)	1.218 (30.94)	0.391 (9.93)	3.020 (76.71)	0.515 (13.08)	±0.031 (0.79)	1.550 (39.37)	6.750 (171.45)
12	3/4	0.672 (17.07)	1.375 (34.93)	0.547 (13.89)	3.230 (82.04)	0.602 (15.29)		1.740 (44.20)	8.000 (203.20)

NOTES:

1. Dimensions are in inches.
2. Metric equivalents are given for general information only.
3. Length of "L" to be with +3% or -1% of specified nominal value.

FIGURE 1. Hose details.

3.7 Finish. Unless otherwise specified, all corrosion-resistant steel fitting components shall be passivated in accordance with SAE AMS-QQ-P-35 prior to assembly. Parts should then be thoroughly rinsed in water and dried.

3.8 Cleanliness.

3.8.1 Cleaning. All hose assemblies shall be free from oil, grease, dirt, moisture, cleaning solvents and other foreign material, both internally and externally.

3.8.2 Closures. Unless otherwise specified, the hose assembly shall be sealed on both ends to prevent foreign matter or moisture from entering during shipping and storage and to prohibit installation unless the closure is removed. Closures shall be constructed to withstand the normal strains, jars, vibrations and other conditions incident to shipping, storage and handling. Closures shall not chip or shred when installed and removed.

3.9 Workmanship. The hose assembly, including all parts, shall be uniform in quality and free from irregularities or defects which could adversely affect safety, performance, reliability, or durability. All surfaces shall be smooth and free from burrs.

3.10 Recycled, recovered, or environmentally preferable materials. Recycled, recovered, or environmentally preferable materials should be used to the maximum extent possible provided that the material meets or exceeds the operational and maintenance requirements, and promotes economically advantageous life cycle costs.

4. VERIFICATION

4.1 Classification of inspection. The inspection requirements specified herein are classified as follows:

- a. First article inspection (see 4.3).
- b. Conformance inspection (see 4.4).

4.2 Cross-reference matrix. Table I provides a cross-reference matrix of the section 3 requirements tested or verified in the paragraphs below.

4.2.1 Component and material inspection. Components and materials shall be inspected in accordance with all the requirements specified herein and in applicable referenced documents.

TABLE I. Cross-reference matrix.

Examination or test	Requirement	Verification	Examination or test	Requirement	Verification
First article	3.1	4.3, 4.3.1, 4.3.1.1, 4.3.1.2	Visual examination	3.4.1.1	4.6.1.1
Materials	3.2	4.6.1.1	Dimensional check	3.4.1.2	4.6.1.2
Hazardous substances	3.2.1	4.6.1.1	Proof pressure	3.4.2	4.6.2
Fungus proof materials	3.2.2	4.6.1.1	Leakage	3.4.3	4.6.3
Rubber products	3.2.3	4.6.1.1	Cold temperature flexing	3.4.4	4.6.4
Dissimilar metal	3.2.4	4.6.1.1	Elongation and contraction	3.4.5	4.6.5
Design and construction	3.3	4.6.1.1	Tensile strength	3.4.6	4.6.6
Hose	3.3.1	4.6.1.1	Burst pressure	3.4.7	4.6.7
Inner tube	3.3.1.1	4.6.1.1	Overtightening torque	3.4.8	4.6.8
Reinforcement	3.3.1.2	4.6.1.1	Pressure impulse cycling	3.4.9	4.6.9
Outer protective cover	3.3.1.3	4.6.1.1	Screw threads	3.5	4.6.1.1
Diameter	3.3.1.4	4.6.1.1, 4.6.1.2	Identification of product	3.6	4.6.1.1
Length	3.3.1.5	4.6.1.1, 4.6.1.2, 4.4.2.2	Finish	3.7	4.4.2
End fittings	3.3.2	4.6.1.1	Cleanliness	3.8	4.6.10
Jump sizes	3.3.3	4.6.1.2	Cleaning	3.8.1	4.5.2
Fitting guard	3.3.4	4.6.1.1	Closures	3.8.2	4.6.1.1
Visual examination and dimensional check	3.4.1	4.6.1, 4.6.1.1, 4.6.1.2	Workmanship	3.9	4.6.1.1

4.3 First article inspection. First article inspection shall consist of examinations and tests as specified in table II performed on samples which are representative of the production item after award of contract, to determine that the production item meets the requirements of this specification.

4.3.1 First article samples. Unless otherwise specified, after award of the contract or order, the manufacturer shall forward six hose assemblies, 24 ± 6 inches (609.6 ± 152.4 mm) long, fabricated from random samples of the bulk hose and end fittings. Samples for the tensile and burst pressure tests may be reduced to a 12 inch (304.8 mm) length to accommodate test equipment, if necessary. The samples shall be representative of the construction, workmanship, components, and materials to be used during production. When a manufacturer is in continuous production of the hose assemblies from one contract to another, submission of additional first article samples for a new contract may be waived at the discretion of the acquiring activity (see 6.2). Approval of the first article samples or the waiving of first article inspection does not preclude the requirements for performing conformance inspection. First article samples shall be furnished to the Government as directed by the contracting officer (see 6.2).

4.3.1.1 First article information. Upon completion of first article inspection, the Government activity responsible for conducting the inspection program (see 6.2), shall report the results of the inspection, with appropriate recommendation, to the contracting officer.

4.3.1.2 Disposition of samples. Upon completion of first article inspection, one approved sample shall be returned to the manufacturer for use in monitoring production; the other samples shall not be returned due to their having been destroyed during testing.

4.4 Conformance inspection. Conformance inspection shall consist of individual tests and sampling tests. Any design or modification of the contractor's standard product to comply with specified requirements shall receive particular attention for adequacy and suitability. Noncompliance with any specified requirements or presence of one or more defects preventing or lessening maximum efficiency shall constitute cause for rejection.

TABLE II. First article inspection.

Inspection	Test method	Sample number ^{1/}					
		1	2	3	4	5	6
Visual examination	4.6.1.1	X	X	X	X	X	X
Dimensional check	4.6.1.2	X	X	X	X	X	X
Cleanliness	4.6.10	X	X				
Proof pressure	4.6.2	X	X	X	X	X	X
Leakage	4.6.3	X	X	X	X	X	X
Cold temperature flexing	4.6.4	X	X				
Elongation and contraction	4.6.5	X	X				
Tensile strength	4.6.6			X	X		
Burst pressure	4.6.7			X	X		
Overtightening torque	4.6.8	X	X				
Pressure impulse cycling	4.6.9					X	X

^{1/} An "X" in sample number column indicates test to be performed on sample.

4.4.1 Individual tests. Each hose assembly shall be subjected to the following tests:

- a. Visual examination and dimensional check.
- b. Proof pressure (without the 160°F conditioning period).
- c. Leakage.

4.4.2 Sampling tests.

4.4.2.1 Lot. A lot shall consist of hose assemblies manufactured under essentially the same conditions and submitted for inspection at substantially the same time.

4.4.2.2 Sampling. For each lot of five hundred hose assemblies or fraction thereof produced, four hose assembly samples, 18 ± 6 inches long, shall be fabricated from random samples of the bulk hose and end fittings using production processes and procedures.

4.4.2.3 Tests. The four hose assemblies, selected from each lot, shall be examined and tested as specified in table III (listed sequence mandatory).

TABLE III. Sampling tests.

Inspection	Test method	Sample number 1/			
		1	2	3	4
Dimensional check	4.6.1.2	X	X	X	X
Cleanliness	4.6.10	X	X		
Proof pressure	4.6.2	X	X	X	X
Leakage	4.6.3	X	X	X	X
Tensile strength	4.6.6	X	X		
Burst pressure	4.6.7	X	X		
Pressure impulse cycling	4.6.9			X	X

1/ An "X" in sample number column indicates test to be performed on sample.

4.5 Test conditions.

4.5.1 Gas. Unless otherwise specified, the gas used for testing, purging or drying the hose assemblies shall be clean, dry, oil-free air or nitrogen having a dew point at 0 psig of not more than 30°F and contain not more than 3 parts per million (ppm) by volume of total hydrocarbons expressed as methane equivalent.

4.5.2 Test fluid. Unless otherwise specified, the fluid used for testing, cleaning and flushing the hose assembly shall be clean, grease free, demineralized water having a specific resistance of not less than 50,000 ohms and suspended or dissolved impurities exceeding 50 ppm.

4.5.3 Temperature and pressure. Unless otherwise specified, tests shall be conducted at local ambient temperature and barometric pressure. The temperature and barometric pressure shall be recorded at the time of inspection. This information shall be available for computation of test data, where required to normal temperature and pressure (NTP) conditions. NTP conditions are 29.92 inches (759.97 mm) of mercury (101.3 kPa) and 70°F (21.1°C). Test instruments shall be calibrated or adjusted according to their required usage in conducting tests.

4.5.4 Instrumentation.

4.5.4.1 Pressures. Pressures and pressure differentials shall be measured by means of Bourdon-type gages or other pressure sensing device. The pressure gage shall have an accuracy of one percent of scale reading.

4.5.4.2 Temperatures. Temperatures shall be measured by appropriately located thermometers or thermocouples used with calibrated potentiometers. The thermometers or thermocouples shall have accuracy within 2°F.

4.6 Inspection methods.

4.6.1 Visual examination and dimensional check.

4.6.1.1 Visual examination. The hose assembly shall be visually examined to ascertain whether both ends are firmly sealed with a protective device and to determine conformance with respect to materials, configuration and workmanship. The hose assembly shall meet the requirements specified in 3.4.1.1.

4.6.1.2 Dimensional check. The hose assembly shall be checked dimensionally to determine conformance to the requirements specified in 3.4.1.2.

4.6.2 Proof pressure. The hose assembly shall be conditioned at not less than 160°F for a minimum of one hour. Immediately after the conditioning period, the hose assembly shall be subjected to 8,000 psig hydrostatic pressure for not less than 30 seconds or exceeding 5 minutes. The hose assembly shall meet the requirements specified in 3.4.2.

4.6.3 Leakage. The hose assembly shall be pressurized to 4,000 psig pneumatic pressure, see 4.4.1, with the assembly under water. The pressure shall be maintained for not less than 1 minute nor more than 15 minutes. The hose assembly shall meet the requirements specified in 3.4.3. Indication of rapid forming and breaking away of bubbles from any point on the outer surface of the hose or any part of the end fitting shall be considered as not meeting the requirements. In the event of a dispute, the effusion from any 12-inch section of the hose assembly shall be collected in an inverted graduate for 15 minutes. At the end of 15 minutes, the amount of gas accumulated in the graduate shall not exceed 50 cc.

4.6.4 Cold temperature flexing. The hose assembly shall be placed in a cold chamber and soaked at $-65 \pm 2^\circ\text{F}$ for a minimum of 24 hours. At the end of the soaking period, and with the hose assembly still at the specified temperature, the hose assembly shall be flexed through 180° to the applicable bend radius shown on figure 1 and then straightened. The hose assembly shall again be flexed through 180° to the same bend radius in such a direction that the portion of the hose under maximum compression during the first flexing will be under maximum expansion during the second flexing. The hose assembly shall be flexed in both directions within 4 seconds. The hose assembly shall meet the requirements specified in 3.4.4. The hose assembly shall then be subjected to and meet the leakage test.

4.6.5 Elongation and contraction. The hose assembly shall be placed in a straight position with one end unrestrained. Before applying pressure, the free length of the hose assembly shall be measured. The hose assembly shall then be pressurized to a minimum of 4,000 psig and maintained at that pressure for a minimum of 5 minutes. At the end of 5 minutes and while still at the test pressure, the change in free length shall be measured. The hose assembly shall meet the requirements specified in 3.4.5.

4.6.6 Tensile strength. The hose assembly shall be placed in a straight position and pressurized to a minimum of 4,000 psig. While pressurized, the hose assembly shall be pulled by the end fittings to a minimum of 1,000 pounds tensile pull at the minimum rate of 1 inch per minute. The hose assembly shall meet the requirements specified in 3.4.6.

4.6.7 Burst pressure. The hose assembly shall be conditioned at not less than 160°F for a minimum of one hour. Immediately after the conditioning period, the hose assembly shall be connected to a pressure source and placed in a straight position with one end unrestrained. The hose assembly shall then be pressurized at a rate of $20,000 \pm 5000$ psi per minute to a maximum pressure of 16,000 psi, held for 1 minute, and then pressurized until failure occurs. The hose assembly shall meet the requirements specified in 3.4.7.

4.6.8 Overtightening torque. The flared end fittings of the hose assembly shall be assembled on a steel fitting conforming to SAE AS4395. The fitting shall be tightened to a minimum overtight-torque of 1-3/4 times the maximum values specified on SAE ARP908 for steel, and loosened. The tightening and loosening sequence shall be repeated until a total of not less than 15 cycles have been performed. The end fitting shall then be removed and examined for damage. The hose assembly shall meet the requirements specified in 3.4.8.

4.6.9 Pressure impulse cycling. The hose assembly shall be subjected to the following tests:

4.6.9.1 Ambient temperature pressure impulse cycling. The hose assembly shall be fixed in a semicircular position with the longitudinal axes of the end fittings parallel. The hose assembly shall be subjected to a hydraulic or pneumatic pressure impulse cycle from 0 to 4,000 to 0 psig at the rate of not less than 60 ± 10 cpm for not less than 1,000 cycles. The hose assembly shall meet the requirements specified in 3.4.9. The hose assembly shall then be subjected to and meet the leakage test.

4.6.9.2 Elevated temperature pressure impulse cycling. The hose assembly shall be subjected to the pressure impulse cycling test specified in 4.6.9.1, except the temperature shall be not less than 160°F. The hose assembly shall meet the requirements specified in 3.4.9. The hose assembly shall then be subjected to and meet the leakage test.

4.6.10 Cleanliness. Fill the hose assembly with clean water or isopropyl alcohol. Using a clean brush, having a diameter at least 1/16 inch (1.59 mm) larger than the inside diameter of the hose, brush the entire internal length of the hose assembly including the end fittings making sure the entire internal surface of the hose assembly is brushed. After the brushing operation, the fluid shall be drained from the hose assembly into a clean beaker. Vigorously agitate the fluid in the beaker before transferring 50 ± 5 cc of the fluid to a clean evaporating dish that has been previously weighed. Evaporate to dryness at $219 \pm 2^\circ\text{F}$. Determine weight of residue and examine residue microscopically for particle size. The hose assembly shall meet the requirements specified in 3.4.10. Upon completion of this test procedure, the hose shall be dried by passing 160°F (maximum) nitrogen gas through the hose.

5. PACKAGING

5.1 Packaging. For acquisition purposes, the packaging requirements shall be as specified in the contract or order (see 6.2). When actual packaging of materiel is to be performed by DoD or in-house contractor personnel, these personnel need to contact the responsible packaging activity to ascertain packaging requirements. Packaging requirements are maintained by the Inventory Control Point's packaging activities within the Military Service or Defense Agency, or within the Military Service's System Command. Packaging data retrieval is available from the managing Military Department's or Defense Agency's automated packaging files, CD-ROM products, or by contacting the responsible packaging activity.

6. NOTES

(This section contains information of a general or explanatory nature that may be helpful, but is not mandatory.)

6.1 Intended use. The hose assembly covered by this specification is intended for use as a component of high-pressure pneumatic ground support equipment used in aircraft ground servicing and engine starting applications. The hose assembly is military unique because it must have a minimum tensile strength of 1,000 pounds and must be able to operate satisfactorily at -65°F . Commercial hoses do not have these requirements. (DO NOT USE FOR OXYGEN.)

6.2 Acquisition requirements. Acquisition documents should specify the following:

- a. Title, number, and date of this specification.
- b. Issue of ASSIST to be cited in the solicitation, and if required, the specific issue of individual documents referenced (see 2.2.1 and 2.3).
- c. Applicable hose assembly size (see 3.3.1.4 and figure 1).

- d. Required length of hose assembly (see 3.3.1.5 and figure 1).
- e. Whether end fitting jump size is required and if on one end or both ends (see 3.3.3).
- f. Whether fitting guard is required (see 3.3.4).
- g. Quantity required.
- h. Whether first article inspection is waived (see 4.3).
- i. Name and address of the first article inspection test facility to which first article samples are to be forwarded (see 4.3.1) and the name and address of the Government activity responsible for conducting the first article inspection program (see 4.3.1.1 and 6.3).
- j. Packaging requirements (see 5.1).

6.3 First article. When a first article inspection is required, the item (s) should be a first article sample. The contracting officer should include specific instructions in acquisition documents regarding arrangements for examinations, approval of first article test results, and disposition of first articles. Invitations for bids should provide that the Government reserves the right to waive the requirement for samples for first article inspection to those bidders offering a product which has been previously acquired or tested by the Government, and that bidders offering such products, who wish to rely on such production or test, must furnish evidence with the bid that prior Government approval is presently appropriate for the pending contract.

6.4 Subject term (key word) listing.

End fitting
Fitting guard
Inner tube
Low temperature
Oil resistant
Ozone resistant

6.5 International system of units (SI). The FED-STD-376, Preferred Metric Units For General Use by the Federal Government - A Guide to the Use of SI, the International System of Units, was used for the conversion to the SI units in this document. The following conversion factors are applicable to this specification.

Foot X 0.3048	=	Meter (m)
Pounds per square inch (psi) X 6.894	=	Kilopascals (kPa)
Degrees Fahrenheit (°F)	=	Degrees Celsius (°C) X 1.8 + 32
Inches X 25.4	=	Millimeters (mm)
Pounds X 0.454	=	Kilograms (kg)

6.6 Environmentally preferable material. Environmentally preferable materials should be used to the maximum extent possible to meet the requirements of this specification. Table IV lists the Environmental Protection Agency (EPA) top seventeen hazardous materials targeted for major usage reduction. Use of these materials should be minimized or eliminated unless needed to meet the requirements specified herein (see section 3).

TABLE IV. EPA top seventeen hazardous materials.

Benzene	Dichloromethane	Tetrachloroethylene
Cadmium and Compounds	Lead and Compounds	Toluene
Carbon Tetrachloride	Mercury and Compounds	1,1,1 – Trichloroethane
Chloroform	Methyl Ethyl Ketone	Trichloroethylene
Chromium and Compounds	Methyl Isobutyl Ketone	Xylenes
Cyanide and Compounds	Nickel and Compounds	

6.7 Guidance on use of alternative parts with less hazardous or nonhazardous materials. This specification provides for a number of alternative plating materials via the PIN. Users should select the PIN with the least hazardous material that meets the form, fit, and function requirements of their application.

6.8 Shelf life. This specification covers items where shelf life is a consideration. Specific shelf-life requirements should be specified in the contract or purchase order. The shelf-life codes are contained in the Federal Logistics Information System Total Item Record. Additive information for shelf-life management may be obtained from DoD 4140.27-M, Shelf-life Management Manual, or the designated shelf-life Points of Contact (POC). The POC should be contacted in the following order. (1) the Inventory Control Points (ICPs), and (2) the DoD Service and Agency Administrators for the DoD Shelf-Life Program. Appropriate POCs for DoD Shelf-Life Program can be contacted through the DoD Shelf-Life Management website: <http://www.shelflife.hq.dla.mil/>.

6.9 Changes from previous issues. Marginal notations are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.

CONCLUDING MATERIAL

Custodians:

Army - AR
Air Force - 99
Navy - SH
DLA - CC

Preparing activity:

DLA - CC

(Project 4720-0399-000)

Review activities:

Army - AT, MI
Air Force - 70
Navy - AS, MC, SA

NOTE: The activities listed above were interested in this document as of the date of this document. Since organizations and responsibilities can change, you should verify the currency of the information above using the ASSIST Online database at <http://www.dodssp.daps.mil/>.