

17 March 1977

SUPERSEDING

MIL-W-81381/10D

15 November 1972

MILITARY SPECIFICATION SHEET

WIRE, ELECTRIC, FLUOROCARBON/POLYIMIDE INSULATED, LIGHT WEIGHT, NICKEL COATED HIGH STRENGTH COPPER ALLOY CONDUCTOR, 600 VOLTS, 200°C, NOMINAL 5.8 MIL WALL.

This specification is approved for use by all Departments and Agencies of the Department of Defense.

The complete requirements for procuring the wire described herein shall consist of this document and the issue in effect of Specification MIL-W-81381.

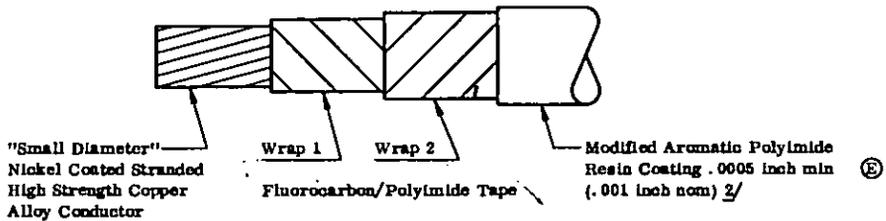


TABLE I. Construction details.

Part Number 1/	Wire Size	Conductor		Finished Wire			Insulation Tapes				
		Stranding (Number of Strands X AWG gage of strands)	Diameter (inches)		Resistance at 20°C (68°F) (ohms/1000 ft) (max)	Diameter (inches) (min-max)	Weight (lbs/1000 ft) (max)	Wrap 1		Wrap 2	
			(min)	(max)				Tape Code 3/	Over- lap (%) (min)	Tape Code 3/	Over- lap (%) (min)
M81381/10-30-*	30	7 x 38	.011	.013	129.6	.023-.027	0.7	.1/1/.1	50	.1/1/.1	50
M81381/10-28-*	28	7 x 36	.014	.016	79.0	.026-.030	1.0				
M81381/10-26-*	26	19 x 38	.018	.020	49.4	.031-.034	1.4				
M81381/10-24-*	24	19 x 36	.023	.025	30.1	.034-.037	2.0				
M81381/10-22-*	22	19 x 34	.029	.031	18.6	.041-.044	3.0				
M81381/10-20-*	20	19 x 32	.037	.040	11.4	.049-.052	4.6				

1/ Part Number: The asterisks in the part number column, Tables I and II, shall be replaced by color code designators in accordance with MIL-STD-681, except that opaque dark yellow as defined in MIL-W-81381 shall be designated by the letter "N" and unpigmented polyimide resin coating shall be designated by the letter "C". Examples: Size 20, opaque dark yellow - M81381/10-20-N; same with orange stripe - M81381/10-20-N3.

2/ Nominal values are for information only. Nominal values are not requirements.

3/ Tape Code: .1/1/.1 0.1 mil FEP fluorocarbon resin/1 mil polyimide film/0.1 mil FEP fluorocarbon resin

FEP = Fluorinated Ethylene Propylene

ⓔ denotes changes.

TABLE II. Performance details.

Part Number	Durability Test Load for		Abrasion Resistance				Bend Testing				
			Weight Support Bracket	Weight (lbs)	Tension Load (lbs)	Resistance (inches of tape) (min)	Mandrel diameter (inches) ($\pm 3\%$)			Test Load (lbs) ($\pm 3\%$)	
	Color Markings (grams)	Insulation Coatings (lbs)					Life Cycle (Oven & bend tests) ^{1/}	Cold Bend Test	Wrap Test	Wrinkle Test ^(E)	Life Cycle (Oven & bend tests) ^{1/}
^(E) M81381/10-30-*	50	.25	A	.125	1.0	21	.250	.125	.125	.50	
^(E) M81381/10-28-*	50	.25	A	.125	1.0	21	.250	.125	.125	.50	
M81381/10-26-*	75	.50	A	.125	1.0	24	.250	.125	.125	.50	
M81381/10-24-*	75	.75	A	.125	1.0	24	.250	.125	.125	.50	
M81381/10-22-*	100	1.00	A	.125	1.0	24	.250	.125	.156	.50	
M81381/10-20-*	100	1.00	A	.125	1.0	24	.250	.125	.188	.75	

^{1/} Also for bend tests after immersion

WIRE RATINGS AND ADDITIONAL REQUIREMENTS

TEMPERATURE RATING: 200°C (392°F) max conductor temperature

VOLTAGE RATING: 600 volts (rms) at sea level

BLOCKING: Oven temperature, 200 \pm 2°C (392 \pm 3.6°F)

COLOR: As specified in contract or order in accordance with MIL-W-81381

FLAMMABILITY: 3 sec (max) after-flame

3.0 inches (max) flame travel

No flaming of tissue paper

HUMIDITY RESISTANCE: 5 megohms-1000 ft, min insulation resistance after humidity exposure

IDENTIFICATION OF PRODUCT: Required for sizes 22 and larger

IDENTIFICATION, STRIPING, OR BANDING DURABILITY: 125 cycles (250 strokes); see Table II for test load

IMPULSE DIELECTRIC TEST: 100% test; impulse voltage as specified in MIL-W-81381

INSULATION RESISTANCE: 2500 megohms-1000 ft (min)

LAMINATION SEALING: Oven temperature, 230 \pm 2°C (446 \pm 3.6°F)

LIFE CYCLE: Oven temperature, 230 \pm 2°C (446 \pm 3.6°F) for 500 hours

MINIMUM WALL THICKNESS: 5.0 mils

POLYIMIDE CURE TEST: Applicable

PROPELLANT RESISTANCE: Test not required

RESIN COATING DURABILITY: 250 cycles (500 strokes); see Table II for test load

SHRINKAGE: 0.031 inch (max) at 230 \pm 2°C (446 \pm 3.6°F)

SURFACE RESISTANCE: 5 megohms-inches (min), initial and final readings

THERMAL SHOCK: Oven temperature, 200 \pm 2°C (392 \pm 3.6°F) Change in measurement, 0.031 inch (max)

WET DIELECTRIC TEST: 2500 volts (rms)

- ^(E) WRINKLE TEST: No wrinkles shall be visible in the insulation at 3X magnification (3 diameters) after bending the wire one full turn around the mandrel specified in Table II. (The wire may be examined on the mandrel or after removal of the mandrel leaving the coil intact.) This test shall be included in the MIL-W-81381 quality conformance inspection as a Group II characteristic, one specimen to be tested from each sample unit.

Intended use note: The wire of this specification sheet is intended for hookup applications in electronic chassis. It is also intended for use in bundles under a protective jacket for interconnecting applications; e.g., in airframes.

Caution: This wire should not be subjected to physical contact with missile propellants.

Custodians:
Navy - AS
Army - EL
Air Force - 11

Review activities:
Navy - EC, SH
Army - MI
Air Force - 99
DSA - IS
NSA

Preparing activity:
Navy - AS
(Project No. 6145-0705-4)

User activities:
Navy - MC, OS
Army - AT, AV, MU

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions - Reverse Side)

1. DOCUMENT NUMBER

2. DOCUMENT TITLE

3a. NAME OF SUBMITTING ORGANIZATION

4. TYPE OF ORGANIZATION (Mark one)

VENDOR

USER

MANUFACTURER

OTHER (Specify): _____

b. ADDRESS (Street, City, State, ZIP Code)

5. PROBLEM AREAS

a. Paragraph Number and Wording:

b. Recommended Wording:

c. Reason/Rationale for Recommendation:

6. REMARKS

7a. NAME OF SUBMITTER (Last, First, MI) - Optional

b. WORK TELEPHONE NUMBER (Include Area Code) - Optional

c. MAILING ADDRESS (Street, City, State, ZIP Code) - Optional

8. DATE OF SUBMISSION (YYMMDD)

(TO DETACH THIS FORM, CUT ALONG THIS LINE.)

INSTRUCTIONS: In a continuing effort to make our standardization documents better, the DoD provides this form for use in submitting comments and suggestions for improvements. All users of military standardization documents are invited to provide suggestions. This form may be detached, folded along the lines indicated, taped along the loose edge (*DO NOT STAPLE*), and mailed. In block 5, be as specific as possible about particular problem areas such as wording which required interpretation, was too rigid, restrictive, loose, ambiguous, or was incompatible, and give proposed wording changes which would alleviate the problems. Enter in block 6 any remarks not related to a specific paragraph of the document. If block 7 is filled out, an acknowledgement will be mailed to you within 30 days to let you know that your comments were received and are being considered.


NOTE: This form may not be used to request copies of documents, nor to request waivers, deviations, or clarification of specification requirements on current contracts. Comments submitted on this form do not constitute or imply authorization to waive any portion of the referenced document(s) or to amend contractual requirements.

(Fold along this line)

(Fold along this line)

DEPARTMENT OF THE NAVY
Commanding Officer
Naval Air Engineering Center
Systems Engineering Standardization Department
(SESD), Code 93
Lakehurst, NJ 08733

OFFICIAL BUSINESS
PENALTY FOR PRIVATE USE \$300



NO POSTAGE
NECESSARY
IF MAILED
IN THE
UNITED STATES

BUSINESS REPLY MAIL
FIRST CLASS PERMIT NO. 12503 WASHINGTON D. C.

POSTAGE WILL BE PAID BY THE DEPARTMENT OF THE NAVY

Commanding Officer
Naval Air Engineering Center
Systems Engineering Standardization Department
(SESD). Code 93
Lakehurst, NJ 08733

ATTN: TJM (9322)

